

# Online Research @ Cardiff

This is an Open Access document downloaded from ORCA, Cardiff University's institutional repository: <http://orca.cf.ac.uk/94193/>

This is the author's version of a work that was submitted to / accepted for publication.

Citation for final published version:

Peneau, Virginie, Shaw, Greg, Armstrong, Robert, Jenkins, Robert Leyshon, Dimitratos, Nikolaos, Taylor, Stuart Hamilton, Zanthoff, Horst, Pietz, Stefan, Stochniol, Guido and Hutchings, Graham John 2016. The partial oxidation of propane under mild aqueous conditions with H<sub>2</sub>O<sub>2</sub> and ZSM-5 catalysts. *Catalysis Science & Technology* 6 (20) , pp. 7521-7531. 10.1039/C6CY01332E file

Publishers page: <http://dx.doi.org/10.1039/C6CY01332E> <<http://dx.doi.org/10.1039/C6CY01332E>>

Please note:

Changes made as a result of publishing processes such as copy-editing, formatting and page numbers may not be reflected in this version. For the definitive version of this publication, please refer to the published source. You are advised to consult the publisher's version if you wish to cite this paper.

This version is being made available in accordance with publisher policies. See <http://orca.cf.ac.uk/policies.html> for usage policies. Copyright and moral rights for publications made available in ORCA are retained by the copyright holders.



# **The Partial Oxidation of Propane under Mild Aqueous Conditions with H<sub>2</sub>O<sub>2</sub> and ZSM-5 Catalysts**

Virginie Peneau<sup>a</sup>, Greg Shaw<sup>a</sup>, Robert D. Armstrong<sup>a</sup>, Robert L. Jenkins<sup>a</sup>, Nikolaos Dimitratos<sup>a</sup>, Stuart H. Taylor<sup>a</sup>, Horst W. Zanthoff<sup>b</sup>, Stefan Peitz<sup>b</sup>, Guido Stochniol<sup>b</sup>, and Graham J. Hutchings<sup>\*a</sup>

<sup>a</sup>Cardiff Catalysis Institute, School of Chemistry, Cardiff University, Main Building, Park Place, Cardiff, CF10 3AT, United Kingdom. Tel: +44 (0) 2920874059, Fax: +44(0) 2090874 030

<sup>b</sup> Evonik Industries AG, 45764 Marl, Germany

\*Corresponding author: Hutch@cf.ac.uk

## Abstract

We report the oxidation of propane under mild aqueous conditions using  $\text{H}_2\text{O}_2$  as the oxidant. Various reaction conditions have been studied with a view to optimising the conversion of propane in the presence of a Fe/ ZSM-5 (30) catalyst. Process optimisation afforded 52% propane conversion in 0.5 h at a temperature of 70 °C.  $\text{C}_3$  products are shown to undergo sequential catalytic C-C scission and oxidation reactions in the presence of the catalysts, yielding  $\text{C}_2$  and  $\text{C}_1$  products. This leads to an inverse relationship between propane conversion and reaction selectivity. Addition of Cu to Fe /ZSM-5 (30) shifted reaction selectivity towards propene ( $\leq 34\%$ ) with increasing conversion.

## 1. Introduction

Increasingly stringent environmental restrictions, depleting crude oil reserves and burgeoning demand are driving the search for alternate, greener routes to bulk chemicals from non-traditional feedstocks. Given their abundance, relatively low cost and global distribution natural and shale gases are promising feedstocks for such a transition, however these are as yet an underutilised resource. Valorisation of the short chain alkane constituents; present within these reserves, is a promising route, however, it is hampered by low substrate reactivity with C-H bond enthalpies in methane ( $\Delta H_{\text{C-H}} = \text{H-CH}_3$  439.6 kJmol<sup>-1</sup>), ethane (H-CH<sub>2</sub>CH<sub>3</sub> 423.3 kJmol<sup>-1</sup>) and propane (H-CH<sub>2</sub>CH<sub>2</sub>CH<sub>3</sub> 422.2/CH<sub>3</sub>CH(H)CH<sub>3</sub> 409.2 kJmol<sup>-1</sup>)[1, 2]. An additional barrier to selective oxidation is that primary reaction products are often more reactive than the substrate, thereby limiting reaction yield. An example of this is the oxidation of propane to acrolein, whereby the weakest C-C bond in acrolein ( $\Delta H_{\text{C-C}} = 347$  kJ mol<sup>-1</sup>) is inherently more reactive than the weakest C-H bonds in either acrolein ( $\Delta H_{\text{C-H}} = 364.4$  kJ mol<sup>-1</sup>) or propane [3]. Consequently, technologies for natural gas upgrading are often energy intensive. A low energy, atom efficient route to the upgrading of these aliphatic hydrocarbons would therefore represent a significant step towards realising the potential of natural gas as a chemical feedstock.

Previously, technologies have focused upon conversion of the lower (C<sub>2</sub> – C<sub>4</sub>) alkanes to their corresponding olefins through steam cracking [4]. Olefins, being intrinsically more reactive than the corresponding alkane, are then converted to value added products. In this way acrolein and acrylic acid are produced commercially from propane via a 2 step process which proceeds through propene [5]. Whilst the oxidation reaction is high yielding, propene production is highly energy intensive and although progress has been made in alternative routes for propene production such as propane dehydrogenation [6], the direct oxidation of propane is preferable [4]. Propene is also an important feedstock for the production of isopropanol [7] and in the cumene process, where benzene is alkylated to yield acetone and phenol. Indeed > 80% of acetone is produced in this way, leading acetone- output to be dictated by global demand for phenol [8]. The direct catalytic transformation of propane to oxygenated products is therefore a growing field of research. Indeed, the direct production of

isopropanol [7, 9], acetone [9, 10], acrylic acid [11-17] and acrolein [18] has been reported. The most promising reactions appear to be propane ammoxidation to acrylonitrile [19] and direct propane oxidation to acrylic acid [20] which have both been trialled at pilot plant scale but are yet to replace existing production routes. However, owing to low liquefaction pressures and low substrate reactivity, the low temperature, liquid phase oxidation of propane has been less extensively studied [7, 9, 21].

A key obstacle to the selective partial oxidation of propane is that high C-H bond energies at both 1° and 2° positions render propane less reactive when compared with its partial oxidation products. Indeed, this is common to the lower alkanes. Therefore, a catalytic system must have sufficiently high rates of C-H activation, whilst inhibiting further oxidation of desirable products. A number of studies have reported the selective oxidation of n-alkanes at low reaction temperatures using the green oxidant H<sub>2</sub>O<sub>2</sub> and MFI- type zeolites [22-32]. ZSM-5 type aluminosilicate zeolites have recently been reported as active catalysts for the oxidation of methane [24, 25] and ethane [22, 23] at temperatures of < 70 °C using H<sub>2</sub>O<sub>2</sub> in the aqueous phase. Catalytic activity was attributed to contaminant iron species present within commercial zeolites (< 100 ppm), which migrate to extraframework positions upon thermal activation to form dimeric μ- oxo- hydroxo iron sites [24]. These sites catalyse H<sub>2</sub>O<sub>2</sub> conversion and also C-H activation reactions, with alkane TOFs (mol<sub>activated</sub> mol<sub>Fe</sub><sup>-1</sup> h<sup>-1</sup>) of greater than 1200 reported [22]. Furthermore, it was reported that simultaneous deposition of post synthesis Fe and Cu onto these catalytically active materials increases productivity and selectivity. In this way reaction selectivity might be tailored to methanol (14.0 mol<sub>methanol formed</sub> kg<sub>cat</sub><sup>-1</sup>h<sup>-1</sup>, 85 % selectivity) from methane, with either acetic acid (25.7 mol<sub>acetic acid formed</sub> kg<sub>cat</sub><sup>-1</sup> h<sup>-1</sup>, 55% selectivity) or ethene (7.8 mol<sub>ethene formed</sub> kg<sub>cat</sub><sup>-1</sup> h<sup>-1</sup>, 34% selectivity) formed from ethane at 50 °C [22, 24]. Alkane activation has also been reported using the titanosilicate zeolite TS-1 [28-32]. Indeed, Shul pin and co-workers reported the selective oxidation of propane, amongst other n-alkanes, with acetone (0.25 mol<sub>acetone</sub> kg<sub>cat</sub><sup>-1</sup> h<sup>-1</sup>) and isopropanol (0.12 mol<sub>isopropanol</sub> kg<sub>cat</sub><sup>-1</sup> h<sup>-1</sup>) being the favoured reaction products [32]. Preferential oxidation of secondary C-H bonds, in particular those adjacent to terminal CH<sub>3</sub> groups in TS-1/ H<sub>2</sub>O<sub>2</sub> alkane oxidation systems, is consistent with previous theoretical [33] and experimental

studies [28, 30]. However, whilst these studies show the reaction to be feasible, failure to address the efficiency of H<sub>2</sub>O<sub>2</sub> use impacts upon atom efficiency and economic viability.

In this study we aim to assess Fe- and Cu- modified ZSM-5 catalysts for activity in the low temperature partial oxidation of propane with H<sub>2</sub>O<sub>2</sub>. A systematic study of reaction conditions targets reaction optimisation. Based on initial findings, catalysts are then selected in order to maximise the yield of partially oxygenated C<sub>3</sub> products

## 2. Experimental

### 2.1 Catalyst preparation

NH<sub>4</sub>-ZSM-5 (SiO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> = 30) was obtained from a commercial source (Zeolyst) and was activated in flowing air prior to use (550 °C, 3 h, 20 °C min<sup>-1</sup>). Where applicable, Fe and/or Cu were deposited to the desired loading by Chemical Vapour Infiltration (CVI) with the appropriate acetylacetonate precursor [34]. This preparation technique has been studied previously, and was shown to give strict control of actual metal loadings [35]. A typical procedure is that prior to the addition of the metal H-ZSM-5 was dried (160 °C, 3 h) under vacuum (10<sup>-3</sup> mbar) prior to sieving (40 mesh). H-ZSM-5 and the appropriate amount of metal acetylacetonate were physically mixed and transferred to a Schlenk flask. The flask was then evacuated (10<sup>-3</sup> mbar) and heated under vacuum (150 °C, 2 h). The sample was removed after cooling to ambient temperature and then calcined in static air (550°C, 3 h, 20 °C min<sup>-1</sup>).

### 2.2 Propane oxidation

Batch catalyst testing for the oxidation of propane with H<sub>2</sub>O<sub>2</sub> was carried out in a 50 ml stainless-steel Parr autoclave fitted with a Teflon liner and a total workable volume of 35 ml. In a typical experiment, the vessel was charged with an aqueous solution of H<sub>2</sub>O<sub>2</sub> (10 ml, 0.5 M, 5000 μmol) and the desired amount of catalyst (typically 27 mg). After purging with helium, the system was charged with propane (4 bar, 4000 μmol) and then the total pressure was increased to 20 bar with helium as

diluent. The autoclave was then heated to the desired reaction temperature (typically 50 °C) and vigorously stirred (1500 rpm) and maintained at a constant temperature for the desired reaction time (typically 0.5 h). After completion of the reaction, the vessel was cooled in ice to *ca.* 12 °C and the gas phase vented into a gas sampling bag. Following this the liquid phase was recovered and filtered prior to analysis.

Liquid products were identified through a combination of <sup>1</sup>H NMR spectroscopy, on a Bruker 500 MHz Ultra-Shield NMR spectrometer (assigned NMR spectra, figure S1), and GC-MS. The products were subsequently quantified against a 1 vol% TMS/CDCl<sub>3</sub> internal standard, which was calibrated against authentic standards of each reaction product using <sup>1</sup>H NMR spectroscopy due to the level of sensitivity required and the use of water as solvent. The <sup>1</sup>H NMR method contained a suppression of the water peak to negate its contribution. Gaseous phase products were analysed using a Varian 450-GC fitted with a CP-Sil 5CB capillary column (50 m length, 0.33 mm ID), a methaniser and FID detector. Products were identified and quantified against standards. The amount of H<sub>2</sub>O<sub>2</sub> remaining after reaction was quantified by titration of aliquots of the final solution against Ce(SO<sub>4</sub>)<sub>2</sub> using Ferroin indicator. This allowed quantification of (a) % H<sub>2</sub>O<sub>2</sub> conversion such that % H<sub>2</sub>O<sub>2</sub> converted =  $((\text{mol}_{\text{start}} - \text{mol}_{\text{end}}) / \text{mol}_{\text{start}} \times 100)$  and (b) % H<sub>2</sub>O<sub>2</sub> utilisation, such that % H<sub>2</sub>O<sub>2</sub> utilised =  $((\text{mol}_o(\text{products}) / \text{mol}_o(\text{converted H}_2\text{O}_2)) \times 100)$

### 3. Results and Discussion

#### 3.1 Preliminary catalyst studies

Previous studies into ZSM-5 catalysed alkane oxidation systems have shown iron impurities within the zeolite framework to be the source of active sites [24]. These migrate to extra-framework sites to form catalytically active dimeric  $\mu$ -oxo-hydroxo iron species upon high temperature activation [24]. From our earlier studies for methane and ethane oxidation, the most intrinsically active catalyst (in terms of TOF mol<sub>Fe</sub><sup>-1</sup> h<sup>-1</sup>) was H-ZSM-5 (SiO<sub>2</sub>:Al<sub>2</sub>O<sub>3</sub> = 30), and hence was investigated for the oxidation of propane under mild reaction conditions ([H<sub>2</sub>O<sub>2</sub>] = 0.5 M, 50°C, 0.5 h). Over the 0.5 h

testing period 0.9 % propane conversion was achieved with 88.7 % selectivity to oxygenated products and the product distribution is shown in Figure 1.

With the aim of increasing propane conversion, iron was deposited post- synthesis onto ZSM-5 by CVI. Fe/ZSM-5 catalysts prepared via this method have been fully characterised previously [23]. HR-TEM has shown that Fe deposits as a porous iron oxide film on the zeolite surface and within its pores [22, 23]. Additionally, UV-Vis spectroscopy indicated the presence of isolated iron clusters, oligomeric iron species, and cationic species at exchange sites within the zeolite pores [22, 23]. The concentration of all Fe species was shown to increase with Fe loading, showing Fe- deposition via CVI to be non-selective [22, 23]. XPS shows the presence of Fe<sup>3+</sup> characteristic of Fe<sub>2</sub>O<sub>3</sub> particles [23].

Deposition of Fe onto H-ZSM-5 led to a significant increase in catalyst productivity relative to H-ZSM-5 (Figure 2). A beneficial effect on propane conversion was observed up to an iron loading of 2.5 wt%, with propane conversion increasing from 0.9% to 7.9%. This constituted a catalyst productivity increase from 2.7 to 23.5 mol<sub>propane converted</sub>·kg<sub>cat</sub><sup>-1</sup>h<sup>-1</sup>. Whilst the oxygenate selectivity remained at *ca.* 90% across this range, the amount of oxygen from converted H<sub>2</sub>O<sub>2</sub> which was utilised in the products increased from 20 to 43%. This is an important result as high efficiency of utilisation is an important economic requirement when using H<sub>2</sub>O<sub>2</sub>. It should however be noted that 43 % utilisation is itself not commercially viable due to economic and safety considerations.

Although catalyst productivity increased with iron loading, the increase was not linear and no further enhancement was observed at loadings of > 2.5 wt%. With increasing Fe loading it is probable that the ion exchange sites within the ZSM-5 framework become increasingly populated with cationic Fe species or blocked by Fe<sub>x</sub>O<sub>y</sub> particles. We have recently reported that iron oxide species on the external zeolite surface are spectator species in the oxidation of ethane using Fe/ZSM-5 catalysts and H<sub>2</sub>O<sub>2</sub> [36]. Figure 2 therefore suggests that Fe species deposited at loadings of > 2.5 wt% behave in much the same way for propane oxidation reactions.

### *3.2 Optimisation of reaction conditions to favour high propane conversion*



To better understand the reaction mechanism, and further increase propane conversion, a systematic study of catalyst testing parameters was conducted using 2.5% Fe/ZSM-5 prepared by CVI.

As shown in Figure 3, propane conversion increased with time up to 0.5 h. However, the rate of propane conversion decreased from 4 h on-line with a maximum of 17.2 % propane converted. With increasing reaction time, a gradual decrease in selectivity to oxygenated products was observed, from 93.6 % at 0.1 h to 89.1% at 6 h, and this corresponded to an increase in CO<sub>2</sub> selectivity of 2.8 % to 4.6 %. A decrease in the rate of reaction at times greater than 4 h is consistent with decreasing availability of H<sub>2</sub>O<sub>2</sub>, indeed 63.9 % H<sub>2</sub>O<sub>2</sub> was converted over the initial 4 hours of reaction. Time on line analysis (Figure 4) shows decreasing selectivity towards the C<sub>3</sub> products propene, n-propanol and isopropanol with increasing reaction time. Meanwhile a corresponding increase in selectivity towards acetic acid, formic acid and CO<sub>2</sub> was observed. Our previous studies into the selective oxidation of ethane over the same catalyst system yielded two primary products (ethanol and ethene) for which analogous C<sub>3</sub> products (n-propanol, isopropanol and propene) were formed (Figure 4) [22]. Hydration of propene is a commercialised route to isopropanol production, and therefore propene is likely to be both a primary and intermediate product to C<sub>3</sub> oxygenated products. Given the high n-propanol and isopropanol selectivities observed at t = 0.1 h, Figure 4 indicates that they are probably both primary products of propane oxidation as well as potential propene oxidation products. The presence of C<sub>2</sub> and C<sub>1</sub>oxygenated products, as well as CO<sub>2</sub> is clear evidence of the catalytic C-C scission of these primary products, and also indicates the presence of carbon centred radical species in solution, consistent with our previous studies [22]. These catalytic transformations are explored in detail later.

The effect of varying [H<sub>2</sub>O<sub>2</sub>], within the range of 0.2 M to 1.8 M, on the propane oxidation was investigated and the results are shown in Figure 5. As expected propane conversion increased with increasing [H<sub>2</sub>O<sub>2</sub>] but oxygenate selectivity remained constant across the whole range at 92% ± 0.8. Above 1.2 M H<sub>2</sub>O<sub>2</sub> an increase to 1.8 M H<sub>2</sub>O<sub>2</sub> led to no increase in conversion which suggests that either the system was propane limited or that competing H<sub>2</sub>O<sub>2</sub> decomposition reactions were limiting oxidant availability. Indeed, the % utilisation of converted H<sub>2</sub>O<sub>2</sub> decreased across the range, from 49.0 % at 0.2 M to 27.0 % at 1.8 M, which suggests that competing H<sub>2</sub>O<sub>2</sub> decomposition reactions become

more favourable in the absence of propane. Such an effect was previously reported for ethane/ H<sub>2</sub>O<sub>2</sub> [36]. An alternate mode of deactivation is through formation of intermediate Fe-OOH species, which previous studies have suggested block access of the alkane substrate to the active site [37]. Moreover, the Fenton's type decomposition of H<sub>2</sub>O<sub>2</sub> leads to a change in the oxidation state of Fe, which could also result in deactivation of the active site for propane [38]. Hence, it is assumed that the low increase of conversion at high H<sub>2</sub>O<sub>2</sub> concentration could be due to H<sub>2</sub>O<sub>2</sub> saturating or deactivating sites that are active for propane activation.

The attainable partial pressure of propane in the current reactor is limited to a P<sub>max</sub> of 4 bar. Therefore under our standard conditions (4 bar propane, 50 °C) Henry's law predicts an aqueous propane concentration of 0.00298 M (Supplementary Figure S2). To determine the reaction order with respect to propane concentration, reactions were carried out at 0.8 and 2 bar propane partial pressure. A pseudo zero order dependence is observed across this pressure range (Figure 6), with the rate of propane conversion showing a slight decrease from 26.0 to 23.5 mol<sub>propane converted</sub> kg<sub>cat</sub><sup>-1</sup> h<sup>-1</sup> upon moving from 0.8 bar (800 μmol<sub>propane</sub>) to 4 bar (4000 μmol<sub>propane</sub>). Consequently, propane conversion increased from 7.9 % to 45.6 % moving from 4 bar to 0.8 bar. Lowering the propane partial pressure from 4 to 0.8 bar led to a decrease in selectivity to primary oxidation products (acetone, isopropanol and n-propanol)(product selectivities not illustrated in Figure 6), indeed total C<sub>3</sub> selectivity decreased from 38.9 % to 22.9%. This was reflected in an increase in selectivity to secondary oxidation products; acetic acid (10.3 % to 21.0%), formic acid (29.1 % to 44.1%) and CO<sub>2</sub> (1.3 % to 5.0%).

Increasing the catalyst mass from 15 mg to 160 mg led to an increase in propane conversion from 5.3 % to 10.9 % over 0.5 h as shown in Figure 7. Increasing the catalyst mass increased the population of active sites available in the reaction, thus increasing the conversion of H<sub>2</sub>O<sub>2</sub> and propane. At the lowest loadings tested (0 – 27 mg) the catalyst operated within the kinetic regime, whilst at loadings of > 27 mg diffusion limitation of H<sub>2</sub>O<sub>2</sub> and/ or propane is implied by a decrease in catalyst productivity (23.5 to 10.6 mol<sub>propane converted</sub> kg<sub>cat</sub><sup>-1</sup> h<sup>-1</sup> for 27 mg and 62 mg respectively). Isopropanol selectivity was observed to decrease with increasing catalyst mass, from 8.4 % at 15 mg loading to 3.7 % with 160 mg of catalyst. Across the same range, selectivity towards n-propanol also decreased from

17.8 to 5.2% respectively, with corresponding increases in formic acid selectivity (24.7 % to 40.5 %) and acetic acid selectivity (8.3 % to 16.9 %). Cracking of primary C<sub>3</sub> to secondary C<sub>2</sub> and C<sub>1</sub> products was clearly catalytic in nature, and these transformations are studied later in this article.

Another approach to increase the rate of propane and H<sub>2</sub>O<sub>2</sub> conversion was through increasing the reaction temperature (Figure 8). Increasing the reaction temperature from 30 to 70 °C afforded an increase in conversion from 1.9% to a  $\chi_{\max}$  of 20.0 %, as shown in Figure 8. Given that 100 % H<sub>2</sub>O<sub>2</sub> conversion was observed within 0.5 h at 90 °C, the effect of further increasing the reaction temperature was not studied. An Arrhenius plot of this data allowed calculation of an activation energy for propane oxidation as 52.7 kJ mol<sup>-1</sup> (Supplementary information Figure S3). The deviation from linearity observed in the Arrhenius plot (70 °C), is probably due to (a) the system becoming oxidant limited, with 87 % H<sub>2</sub>O<sub>2</sub> conversion observed after 0.5 h and (b) competing thermal H<sub>2</sub>O<sub>2</sub> decomposition. Indeed, it is well known that thermal conversion of H<sub>2</sub>O<sub>2</sub> occurs at temperatures of > 60 °C. Selectivity towards C<sub>3</sub> products decreased when increasing the reaction temperature from 30 °C to 70 °C, indeed selectivity to isopropanol decreased from 14.8 % to 2.1 % across this range. A corresponding increase of acetone selectivity, from 3.7 % to 8.6 % is consistent with consecutive oxidation pathways. A significant increase in formic acid selectivity was also observed with increasing temperature, from 13.7 % at 30 °C to a maxima of 43.6 % at 90 °C. These selectivities appear to be inherent of this catalytic reaction system and arise relative to changes in the propane conversion. Therefore, if high C<sub>3</sub> selectivity is to be realised under these testing conditions then operation at low temperatures/ low conversion is preferred. These trends are borne out of conversion vs selectivity plots that are described later.

To optimise propane conversion, reaction conditions were selected to reflect the findings of these systematic studies. The conditions used were; 0.1 g 2.5 wt% Fe / ZSM-5, [H<sub>2</sub>O<sub>2</sub>] = 1 M (10,000  $\mu$ mol), 70 °C (Table 2 Entry 2). Under these conditions 33 % propane conversion was observed after 0.5 h of reaction. Further increasing the reaction time had no beneficial effect upon conversion, as 99 % H<sub>2</sub>O<sub>2</sub> was converted within the initial 0.5 h of reaction and therefore the system was be oxidant limited. However, by lowering the partial pressure of propane to 1 bar *ca.* 52 % conversion was

attained (Table 2 Entry 5). Low C<sub>3</sub> selectivities were observed under these high conversion conditions, with reaction selectivity favouring the secondary oxidation products; acetic acid, formic acid and CO<sub>2</sub>.

Conversion versus selectivity plots were constructed using the combined 2.5 % Fe/ZSM-5 (30) optimisation studies. This provided insight into the catalytic transformations which yielded the observed C<sub>3</sub>, C<sub>2</sub> and C<sub>1</sub> products. (Supplementary Information Figures S4, S5 and S6). Three primary C<sub>3</sub> products were considered possible; n-propanol, isopropanol and propene (Supplementary Information Figure S4). Selectivity to these products decreased with increasing conversion, with corresponding increases in acetone and propanoic acid selectivity. C-C scission is evident, with both C<sub>2</sub> and C<sub>1</sub> products formed. Our previous studies into the oxidation of ethane over ZSM-5 catalysts showed that ethane underwent catalytic transformation to ethanol, ethene and ethylhydroperoxide (EtOOH, not observed here) [22]. These primary products underwent secondary oxidation to acetic acid and C-C scission yielded carbon centred radicals, which were either oxidised to form C<sub>1</sub> products; formic acid, methanol, methylhydroperoxide (MeOOH, not observed here) and CO<sub>2</sub> or recombined to reform ethane [22]. We propose that the C<sub>2</sub> and C<sub>1</sub> oxidation pathways are consistent with previously reported ethane and methane studies [22, 24]. Consistent with a consecutive oxidation/ C-C scission reaction profile, selectivity towards formic acid and CO<sub>2</sub> increased with increasing propane conversion.

To better understand the source of secondary reaction products, the reactivity of C<sub>3</sub> oxygenated products was studied under standard conditions (0.5 M H<sub>2</sub>O<sub>2</sub>, 27 mg 2.5% Fe/ZSM-5 (30), P = 20 bar, 50 °C, 1500 rpm) using an atmosphere of 100 % He. The starting concentration of the products was 0.05 M, which is similar to the concentration range obtained during a reaction. Oxidation of n-propanol gave propanoic acid (30 % selectivity) and formic acid (49 % selectivity) as major products. Meanwhile isopropanol was oxidised to acetone (29 % selectivity), acetic acid (33 % selectivity) and formic acid (36 % selectivity). C-C scission of all C<sub>3</sub> oxygenate products (n-propanol, isopropanol, acetone and propanoic acid) gave acetic acid, formic acid and CO<sub>2</sub> as reported in Table 3. High rates of catalytic conversion of C<sub>3</sub> oxygenated products are shown in Table 3. When compared with the rate

of propane conversion under our standard conditions ( $23.5 \text{ mol}_{\text{propane converted}} \text{ kg}_{\text{cat}}^{-1} \text{ h}^{-1}$ ) it is apparent that high yields of partially oxygenated  $\text{C}_3$  products might not be realised using 2.5 % Fe/ZSM-5 (30), which is consistent with trends in Supplementary Figures S4-S6. These data were used to propose a reaction scheme for the liquid phase oxidation of propane as shown in Figure 9.

Interestingly, the molar rate of  $\text{H}_2\text{O}_2$  conversion ( $\text{mol}_{\text{converted}} \text{ h}^{-1}$ ) correlated differently with increasing propane conversion depending on reaction conditions (Supplementary Information Figure S7). Figure S7 shows that propane conversion might be increased through increasing catalyst mass or reaction time, but that a high degree of propane conversion and relatively low  $\text{H}_2\text{O}_2$  conversion is achieved only at long reaction times. This is likely because increasing the catalyst mass increases, not only the rate of propane activation and  $\text{H}_2\text{O}_2$  utilisation, but also the rate at which  $\text{H}_2\text{O}_2$  is decomposed. Hence, propane activation cannot be correlated with  $\text{H}_2\text{O}_2$  conversion in a generalised way.

### *3.3 Increasing $\text{C}_3$ product selectivity through catalyst development*

Previously, we have shown the promoting effect of the addition of copper towards enhancing selectivity towards primary reaction products in the oxidation of both methane and ethane [22, 24], demonstrating increased selectivity for methanol and ethene respectively. It has been reported that Cu effectively inhibits secondary oxidation pathways by scavenging  $\cdot\text{OH}$  radicals [22, 24, 25, 39]. We therefore investigated whether co-deposition of Fe and Cu onto H-ZSM-5 (30) might produce higher selectivity towards primary  $\text{C}_3$  products. At a constant Fe loading of 1.25 wt%, a decrease of propane conversion was observed with increasing Cu loading. Indeed, propane conversion decreased from 5.9% for 1.25% Fe/ZSM-5 (30) to 2.6 % for 1.25% Fe 2.5% Cu/ZSM-5 (30) as shown in Table 4. Hence, we suppose that the addition of Cu either (i) blocks active iron sites, thus decreasing the capacity of Fe to activate propane or (ii) the Cu sites catalytically terminate oxygen- based radicals, thereby lowering the rate of propane oxidation. Decreased conversion with increasing Cu loading is consistent with propane activation being at least in part a radical based mechanism, with Cu suppressing propane activation through scavenging of oxygen centred radicals ( $\cdot\text{OH}$ ). In this way propane oxidation would be behaving differently from methane oxidation over the same catalysts,

whereby methane was oxidised to MeOOH in a molecular mechanism, with free  $\cdot\text{OH}$  radicals implicated in subsequent oxidation steps only [25]. Total  $\text{C}_3$  product selectivity increased from 38 % for 0 wt% Cu to 71 % at 2.5 wt% Cu loading. Key to this was the change in propene selectivity, which increased from 2% to 34% at 2.5 wt% Cu. (Table 4), with a corresponding decrease in acetic and formic acid selectivities. It can therefore be concluded that supported Cu species suppress the oxidation of propene (a primary product), as they were previously reported to suppress the oxidation of ethene under comparable ethane/  $\text{H}_2\text{O}_2$  oxidation conditions [22]. A comparison of the catalytic performance of H-ZSM-5 (30) and 2.5 % Cu/ZSM-5 (30) prepared by CVI is shown in Supplementary Table S1. It is apparent that deposition of 2.5 wt% Cu has no net benefit upon propane conversion, which actually decreased from 0.9 % to 0.36 % at isoconversion of  $\text{H}_2\text{O}_2$ . Consistent with data in Table 5, post-synthesis deposition of Cu had a significant effect on  $\text{C}_3$  selectivity which increased from 48 to 72 %. Indeed, the product distributions shifts, from that shown in Figure 1 to favour isopropanol (19.8 % selectivity), n-propanol (18.8 %) and propene (21 %) as major reaction products. Our previous EPR studies have shown that ZSM-5 – supported Cu sites catalytically terminate oxygen based radicals in methane / ethane oxidation systems and thereby afford higher selectivity towards primary products, methanol and ethene respectively at isoconversion. It is likely that Cu sites fulfil a similar role within the current propane oxidation reaction. Decreased propane conversion is consistent with data in Table 5 and further suggests that the rate of propane conversion is at least partly dependent upon the concentration of  $\cdot\text{OH}$  radicals. A spectroscopic investigation of the nature of Cu species and their role within this catalytic system will be addressed in a future publication.

To determine whether high  $\text{C}_3$  yields might be realised, 1.25 % Fe 1.25 % Cu/ ZSM-5 (30) was tested under the previously optimised reaction conditions (70 °C, 100 mg catalyst and 1 M  $\text{H}_2\text{O}_2$ ). Results are shown in Table 5. Under optimised reaction conditions (Table 5 Entry 2) 17.6 % propane conversion was observed. The same catalyst gave 3.9 % conversion under standard conditions. With 2.5% Fe/ZSM-5 (30) a significant decrease in  $\text{C}_3$  selectivity (33 % to 17 %) was observed, when changing from standard to optimised reaction conditions (Table 2 Entries 1 and 2).  $\text{C}_3$  selectivity also

decreased for 1.25 % Fe 1.25 % Cu/ZSM-5 (30), from 64 % to 40 % under the same conditions (Table 5 Entries 1 and 2). The full C<sub>3</sub> product selectivity breakdown under optimised conditions was; acetone 11.8%, propene 13.1%, propanoic acid 7.2%, n-propanol 6.3% and isopropanol 2% with a total catalyst productivity of 14 mol<sub>propane converted</sub> kg<sub>cat</sub><sup>-1</sup> h<sup>-1</sup>.

It is important to note that in this study 4 bar (4000μmol) propane was used to ensure that propane was not the limiting reagent. As shown previously with ZSM-5, increased propane conversion might be achieved with no significant loss in catalyst productivity, through decreasing the partial pressure of propane. Future studies will seek to increase C<sub>3</sub> selectivity and the efficiency with which H<sub>2</sub>O<sub>2</sub> is utilised in these zeolite- catalysed systems.

#### **4. Conclusions**

This work demonstrates that propane can be converted selectively into oxygenated products, typically > 95 % selectivity, using H<sub>2</sub>O<sub>2</sub> as the oxidant and MFI zeolite catalysts. The activity of a ZSM-5 zeolite has been increased by post deposition of iron, and reaction conditions optimised to achieve propane conversions of up to 52%. Combined optimisation and mechanistic studies have resulted in the identification of the reaction scheme. The selectivity to specific products achieved is inherently linked to propane conversion in this catalytic reaction. A route to increasing C<sub>3</sub> selectivity has been shown, through addition of Cu to Fe/ZSM-5 (30) to favour propene as a major product (33.7 % selectivity).

#### **5. Acknowledgement**

The authors would like to thank Evonik Industries for financial support.

#### **6. References**

- [1] S.J. Blanksby, G.B. Ellison, Bond dissociation energies of organic molecules, *Accounts Chem. Res.*, 36 (2003) 255-263.
- [2] Y.-R. Luo, *Handbook of Bond Dissociation Energies in Organic Compounds*, CRC Press, 2002.
- [3] C. Batiot, B.K. Hodnett, The role of reactant and product bond energies in determining limitations to selective catalytic oxidations, *Applied Catalysis A: General*, 137 (1996) 179-191.
- [4] N. Rahimi, R. Karimzadeh, Catalytic cracking of hydrocarbons over modified ZSM-5 zeolites to produce light olefins: A review, *Applied Catalysis A: General*, 398 (2011) 1-17.

- [5] R.K. Grasselli, J.D. Burrington, Oxidation of Low-Molecular-Weight Hydrocarbons, in: Handbook of Heterogeneous Catalysis, Wiley-VCH Verlag GmbH & Co. KGaA, 2008.
- [6] M.M. Bhasin, J.H. McCain, B.V. Vora, T. Imai, P.R. Pujadó, Dehydrogenation and oxydehydrogenation of paraffins to olefins, *Applied Catalysis A: General*, 221 (2001) 397-419.
- [7] R. Raja, C.R. Jacob, P. Ratnasamy, Direct oxidation of propane to isopropanol, *Catalysis Today*, 49 (1999) 171-175.
- [8] S. Sifniades, A.B. Levy, H. Bahl, Acetone, in: Ullmann's Encyclopedia of Industrial Chemistry, Wiley-VCH Verlag GmbH & Co. KGaA, 2000.
- [9] F. Frusteri, L. Spadaro, C. Espro, A. Parmaliana, F. Arena, Liquid-phase selective oxidation of propane on silica-supported Nafion catalysts, *J. Nat. Gas Chem.*, 11 (2002) 180-185.
- [10] N.A. Mashayekhi, M.C. Kung, H.H. Kung, Selective oxidation of hydrocarbons on supported Au catalysts, *Catal. Today*, 238 (2014) 74-79.
- [11] E. Balcells, F. Borgmeier, I. Grißtede, H.G. Lintz, Partial Oxidation of Propane and Propene to Acrylic Acid over a Mo-V-Te-Nb Oxide Catalyst, *Catalysis Letters*, 87 (2003) 195-199.
- [12] S. Hernández-Morejudo, A. Massó, E. García-González, P. Concepción, J.M. López Nieto, Preparation, characterization and catalytic behavior for propane partial oxidation of Ga-promoted MoVTeO catalysts, *Applied Catalysis A: General*.
- [13] M. Lin, T.B. Desai, F.W. Kaiser, P.D. Klugherz, Reaction pathways in the selective oxidation of propane over a mixed metal oxide catalyst, *Catalysis Today*, 61 (2000) 223-229.
- [14] M.M. Lin, Selective oxidation of propane to acrylic acid with molecular oxygen, *Applied Catalysis A: General*, 207 (2001) 1-16.
- [15] E.K. Novakova, J.C. Védrine, E.G. Derouane, Propane Oxidation on Mo-V-Sb-Nb Mixed-Oxide Catalysts: 1. Kinetic and Mechanistic Studies, *Journal of Catalysis*, 211 (2002) 226-234.
- [16] M. Sun, J. Zhang, P. Putaj, V. Caps, F. Lefebvre, J. Pelletier, J.-M. Basset, Catalytic Oxidation of Light Alkanes (C1-C4) by Heteropoly Compounds, *Chemical Reviews*, 114 (2014) 981-1019.
- [17] W. Li, K. Oshihara, W. Ueda, Catalytic performance for propane selective oxidation and surface properties of 12-molybdophosphoric acid treated with pyridine, *Appl. Catal., A*, 182 (1999) 357-363.
- [18] T. Mazari, C.R. Marchal, S. Hocine, N. Salhi, C. Rabia, Oxidation of propane over substituted Keggin phosphomolybdate salts, *J. Nat. Gas Chem.*, 18 (2009) 319-324.
- [19] A.T. Guttmann, R.K. Grasselli, J.F. Brazdil, Amoxidation of paraffins and catalysts therefor, in, Google Patents, 1988.
- [20] K. Kadowaki, T. Koshikawa, B. Oshida, Process for production of acrylic acid, in, Google Patents, 1975.
- [21] E.V. Kudrik, P. Afanasiev, D. Bouchu, J.-M.M. Millet, A.B. Sorokin, Diiron N-bridged species bearing phthalocyanine ligand catalyzes oxidation of methane, propane and benzene under mild conditions, *Journal of Porphyrins and Phthalocyanines*, 12 (2008) 1078-1089.
- [22] M.M. Forde, R.D. Armstrong, C. Hammond, Q. He, R.L. Jenkins, S.A. Kondrat, N. Dimitratos, J.A. Lopez-Sanchez, S.H. Taylor, D. Willock, C.J. Kiely, G.J. Hutchings, Partial Oxidation of Ethane to Oxygenates Using Fe- and Cu-Containing ZSM-5, *Journal of the American Chemical Society*, 135 (2013) 11087-11099.
- [23] M.M. Forde, R.D. Armstrong, R. McVicker, P.P. Wells, N. Dimitratos, Q. He, L. Lu, R.L. Jenkins, C. Hammond, J.A. Lopez-Sanchez, C.J. Kiely, G.J. Hutchings, Light alkane oxidation using catalysts prepared by chemical vapour impregnation: tuning alcohol selectivity through catalyst pre-treatment, *Chemical Science*, 5 (2014) 3603-3616.
- [24] C. Hammond, M.M. Forde, M.H.a. Rahim, A. Thetford, Q. He, R.L. Jenkins, N. Dimitratos, J.A. Lopez-Sanchez, N.F. Dummer, D.M. Murphy, A.F. Carley, S.H. Taylor, D.J. Willock, Eric E. Stangland, J. Kang, H. Hagen, C.J. Kiely, G.J. Hutchings, Direct Catalytic Conversion of Methane to Methanol in an Aqueous Medium by using Copper-Promoted Fe-ZSM-5, *Angewandte Communications*, 51 (2012) 5129-5133.
- [25] C. Hammond, R.L. Jenkins, N. Dimitratos, J.A. Lopez-Sanchez, M.H.a. Rahim, M.M. Forde, A. Thetford, D.M. Murphy, H. Hagen, E.E. Stangland, J.M. Moulijn, S.H.T.J. Willock, G.J. Hutchings,



Catalytic and mechanistic insights of the low-temperature selective oxidation of methane over Cu-promoted Fe-ZSM-5, *Chemistry-A European Journal*, 18 (2012) 15735-15745.

[26] A.K.M.L. Rahman, R. Indo, H. Hagiwara, T. Ishihara, Direct conversion of ethane to acetic acid over H-ZSM-5 using H<sub>2</sub>O<sub>2</sub> in aqueous phase, *Applied Catalysis A: General*, 456 (2013) 82-87.

[27] A.K.M.L. Rahman, M. Kumashiro, T. Ishihara, Direct synthesis of formic acid by partial oxidation of methane on H-ZSM-5 solid acid catalyst, *Catalysis Communications*, 12 (2011) 1198-1200.

[28] M.G. Clerici, Oxidation of saturated hydrocarbons with hydrogen peroxide, catalyzed by titanium silicalite, *Appl. Catal.*, 68 (1991) 249-261.

[29] D.R.C. Huybrechts, The oxidation of saturated hydrocarbon chains, in, Exxon Chemical Patents, Inc., USA . 1990, pp. 20 pp.

[30] D.R.C. Huybrechts, L. De Bruycker, P.A. Jacobs, Oxyfunctionalization of alkanes with hydrogen peroxide on titanium silicalite, *Nature (London)*, 345 (1990) 240-242.

[31] C.B. Khouw, C.B. Dartt, J.A. Labinger, M.E. Davis, Studies on the catalytic oxidation of alkanes and alkenes by titanium silicates, *J. Catal.*, 149 (1994) 195-205.

[32] G.B. Shul'pin, T. Sooknoi, V.B. Romakh, G. Suss-Fink, L.S. Shul'pina, Regioselective alkane oxygenation with H<sub>2</sub>O<sub>2</sub> catalyzed by titanosilicalite TS-1, *Tetrahedron Letters* 47 (2006) 3071-3075.

[33] G. Vayssilov, Theoretical Modelling of Propane Partial Oxidation over Titanium Silicalites, in: E. Derouane, J. Haber, F. Lemos, F. Ribeiro, M. Guisnet (Eds.) *Catalytic Activation and Functionalisation of Light Alkanes*, Springer Netherlands, 1998, pp. 439-445.

[34] M.M. Forde, L. Kesavan, M.I.b. Saiman, Q. He, N. Dimitratos, J.A. Lopez-Sanchez, R.L. Jenkins, S.H. Taylor, C.J. Kiely, G.J. Hutchings, High Activity Redox Catalysts Synthesized by Chemical Vapor Impregnation, *ACS Nano*, 8 (2014) 957-969.

[35] M.M. Forde, R.D. Armstrong, R. McVicker, P.P. Wells, N. Dimitratos, Q. He, L. Lu, R.L. Jenkins, C. Hammond, J.A. Lopez-Sanchez, C.J. Kiely, G.J. Hutchings, Light alkane oxidation using catalysts prepared by chemical vapour impregnation: tuning alcohol selectivity through catalyst pre-treatment, *Chemical Science*, 5 (2014) 3603-3616.

[36] R.D. Armstrong, S.J. Freakley, M.M. Forde, V. Peneau, R.L. Jenkins, S.H. Taylor, J.A. Moulijn, D.J. Morgan, G.J. Hutchings, Low temperature catalytic partial oxidation of ethane to oxygenates by Fe- and Cu-ZSM-5 in a continuous flow reactor, *Journal of Catalysis*, 330 (2015) 84-92.

[37] C. Hammond, I. Hermans, N. Dimitratos, Biomimetic Oxidation with Fe-ZSM-5 and H<sub>2</sub>O<sub>2</sub>? Identification of an Active, Extra-Framework Binuclear Core and an Fe<sup>III</sup> OOH Intermediate with Resonance- Enhanced Raman Spectroscopy, *ChemCatChem*, 7 (2015) 434-440.

[38] W.G. Barb, J.H. Baxendale, P. George, K.R. Hargrave, Reactions of Ferrous and Ferric Ions with Hydrogen Peroxide, *Nature*, 163 (1949) 692-694.

[39] C. Hammond, N. Dimitratos, R.L. Jenkins, J.A. Lopez-Sanchez, S.A. Kondrat, M. Hasbi ab Rahim, M.M. Forde, A. Thetford, S.H. Taylor, H. Hagen, E.E. Stangland, J.H. Kang, J.M. Moulijn, D.J. Willock, G.J. Hutchings, Elucidation and Evolution of the Active Component within Cu/Fe/ZSM-5 for Catalytic Methane Oxidation: From Synthesis to Catalysis, *ACS Catalysis*, 3 (2013) 689-699.

[40] J.J. Bravo-Suárez, K.K. Bando, T. Fujitani, S.T. Oyama, Mechanistic study of propane selective oxidation with H<sub>2</sub> and O<sub>2</sub> on Au/TS-1, *Journal of Catalysis*, 257 (2008) 32-42.

[41] J.J. Bravo-Suarez, K.K. Bando, T. Akita, T. Fujitani, T.J. Fuhrer, S.T. Oyama, Propane reacts with O<sub>2</sub> and H<sub>2</sub> on gold supported TS-1 to form oxygenates with high selectivity, *Chem. Commun. (Cambridge, U. K.)*, (2008) 3272-3274.


[42] M. Haruta, S. Tsubota, T. Hayashi, Method for production of alcohol, ketone, and aldehyde by oxidation of hydrocarbon, in, Agency of Industrial Science and Technology, Ministry of International Trade and Industry, Japan . 1996, pp. 9 pp.

[43] B. Kerler, A. Martin, A. Jans, M. Baerns, Partial oxidation of propane in compressed carbon dioxide using CoOx/SiO<sub>2</sub> catalysts, *Applied Catalysis A: General*, 220 (2001) 243-252.


**Table 1** A summary of current literature on the direct catalytic oxidation of propane

Entry	Catalyst	Solvent	Reactor Temp / °C	$P(\text{C}_3\text{H}_8)$ / bar	Oxidant	S (major $\text{C}_3$ products)	Mass normalised rate / mol propane converted $\text{kg cat}^{-1} \text{h}^{-1}$	Total Oxygenate Selectivity / % <sup>[a]</sup>	Ref.
1	TS-1	95% MeOH, 5% $\text{H}_2\text{O}$	55	n.d	$\text{H}_2\text{O}_2$	Acetone (66), <i>i</i> -PrOH (34)	2.25	n.d	[28]
2	TS-1	-	60	5	$\text{H}_2\text{O}_2$	Acetone (68), <i>i</i> -PrOH (32)	0.37	n.d	[32]
3	0.52% Au/TS-1	Gas Phase	170 <sup>[b]</sup>	0.127	$\text{H}_2\text{O}_2$ <sup>[c]</sup>	Acetone (92), <i>i</i> -PrOH (4)	3.17	97.0	[40]
4	0.11% Au- Ba/ TS-1 <sup>[d]</sup>	Gas Phase	170 <sup>[b]</sup>	0.15	$\text{H}_2\text{O}_2$ <sup>[c]</sup>	Acetone (90), <i>i</i> -PrOH (5)	0.63	95.0	[41]
5	Au- $\text{TiO}_2/\text{SiO}_2$	Gas Phase	80 <sup>[b]</sup>	0.05	$\text{H}_2\text{O}_2$ <sup>[c]</sup>	Acetone (59)	0.039	58.8	[42]
6	2.4 wt% $\text{Co}_3\text{O}_4\text{-SiO}_2$	sc $\text{CO}_2$	280	1	$\text{O}_2$	Acetone (7), $\text{C}_3\text{H}_6$ (5)	n.d	49.6	[43]
7	1.25% Fe 1.25% Cu/ZSM-5 (30)	$\text{H}_2\text{O}$	50	4	$\text{H}_2\text{O}_2$	$\text{C}_3\text{H}_6$ (24), <i>n</i> -PrOH (16), <i>i</i> -PrOH (16)	11.6	64.9	Current Article


<sup>[a]</sup> Total oxygenate selectivity where reported, <sup>[b]</sup> Reaction carried out in the gas phase, <sup>[c]</sup>  $\text{H}_2\text{O}_2$  generated *in situ* from  $\text{O}_2$  and  $\text{H}_2$ , <sup>[d]</sup> Ba loading not defined, [n.d] signifies not defined

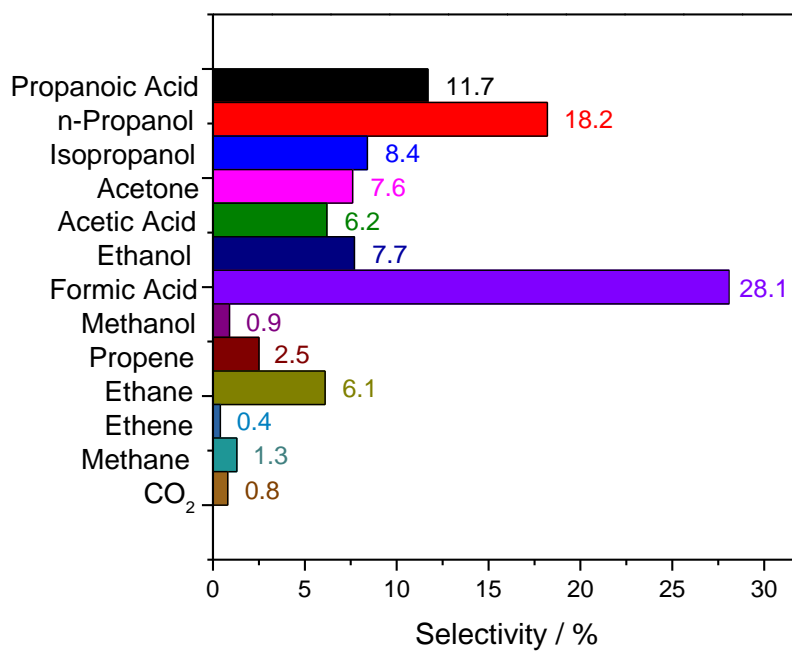


**Figure 1** – The product distribution for a propane oxidation reaction catalysed by H-ZSM-5 (30). Reaction conditions: Propane (4000  $\mu\text{mol}$ ),  $[\text{H}_2\text{O}_2] = 0.5 \text{ M}$  (5000  $\mu\text{mol}$ ), 27 mg H-ZSM-5 (30), 50  $^\circ\text{C}$ , 0.5 h, 1500 rpm.

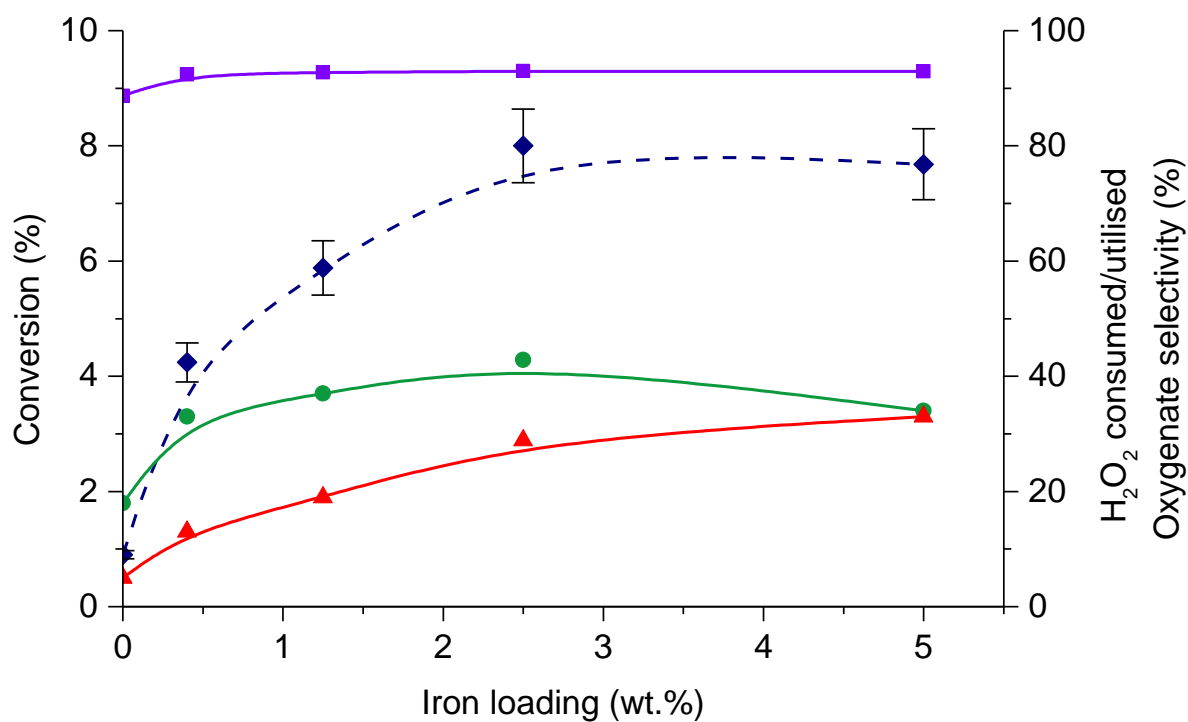

**Figure 2** – Effect of Fe loading for propane oxidation. Propane conversion (◆), oxygenate selectivity (■), H<sub>2</sub>O<sub>2</sub> converted (▲) and H<sub>2</sub>O<sub>2</sub> utilised (●). Reaction conditions: Propane (4000 μmol), [H<sub>2</sub>O<sub>2</sub>] = 0.5 M (5000 μmol), catalyst (27 mg), 50 °C, 0.5 h, 1500 rpm.

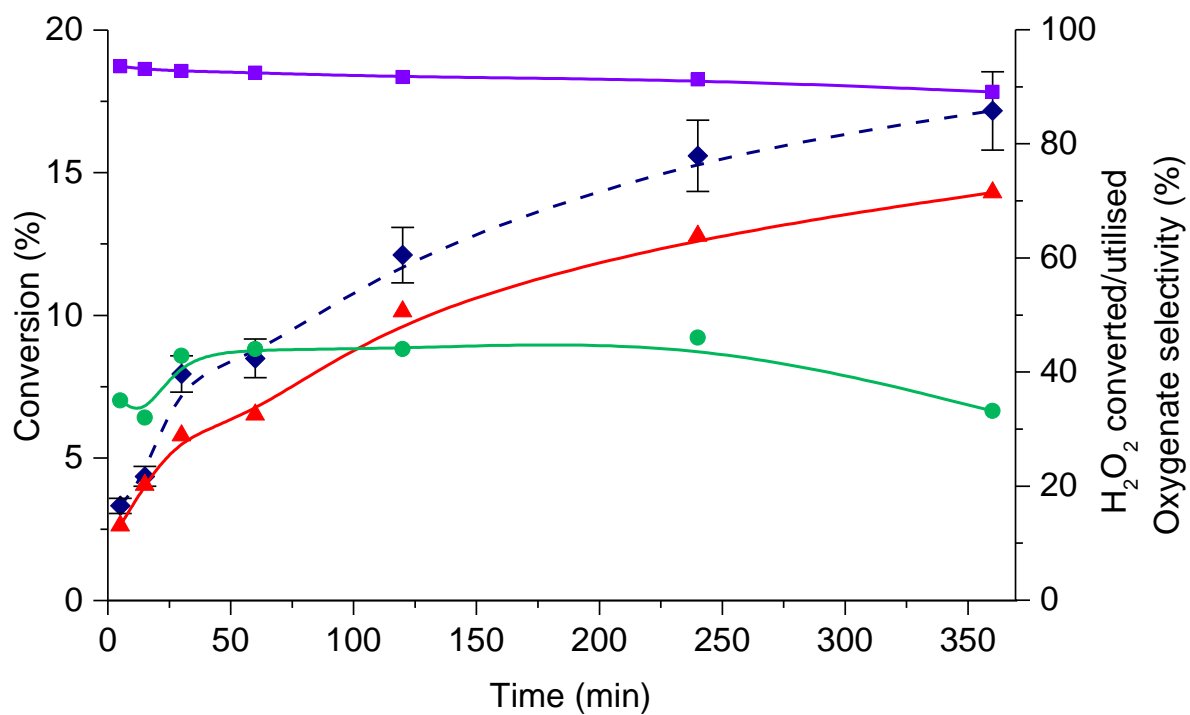

**Figure 3** – Effect of time for propane oxidation. Propane conversion (◆), oxygenate selectivity (■), H<sub>2</sub>O<sub>2</sub> converted (▲) and H<sub>2</sub>O<sub>2</sub> utilised (●). Reaction conditions: Propane (4000 μmol), [H<sub>2</sub>O<sub>2</sub>] = 0.5 M (5000 μmol), 2.5 % Fe/ZSM-5 (30) (27 mg), 50 °C, 1500 rpm.

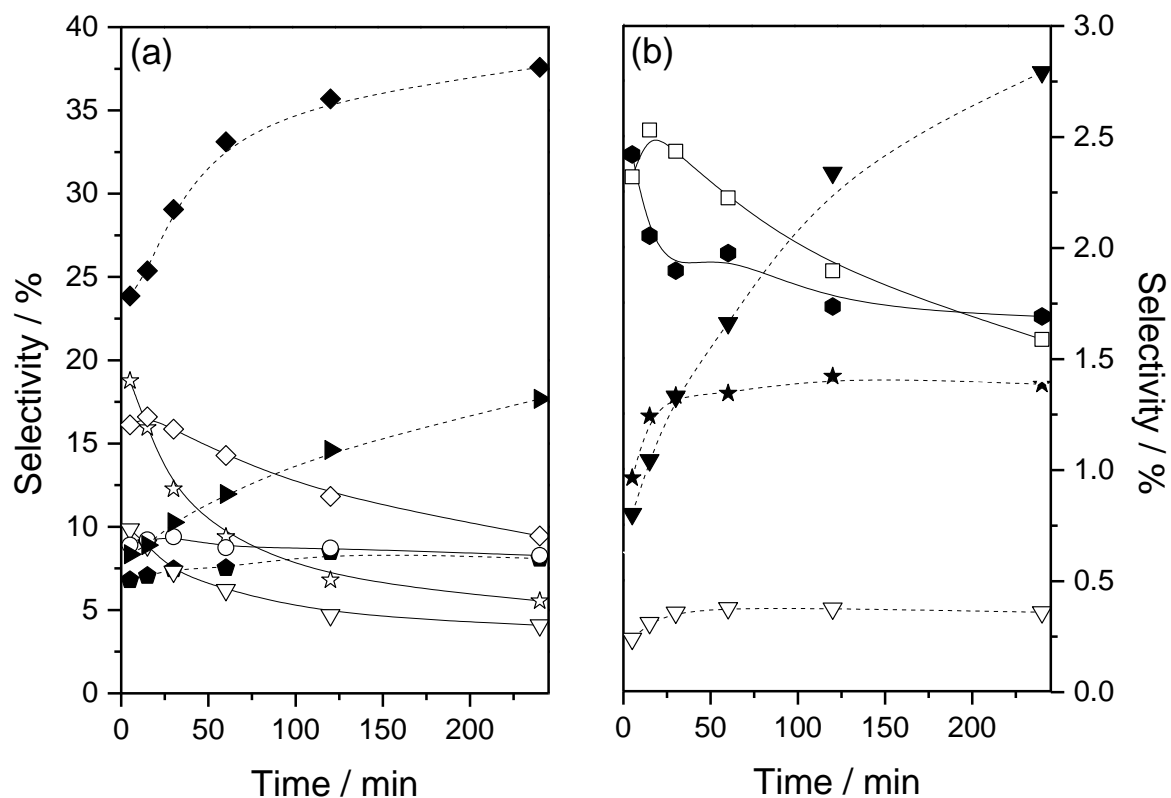


**Figure 4** – Temporal evolution of propane oxidation reaction products.


(a) Major reaction products: formic acid (◆), acetic acid (▶), ethanol (◇), n-propanol (☆), propanoic acid (○), acetone (●) and isopropanol (▽).

(b) Minor reaction products:  $\text{CO}_2$  (▼),  $\text{C}_3\text{H}_6$  (□),  $\text{C}_2\text{H}_6$  (●), methanol (★) and  $\text{C}_2\text{H}_4$  (▽).

Reaction conditions: Propane (4000  $\mu\text{mol}$ ),  $[\text{H}_2\text{O}_2] = 0.5 \text{ M}$  (5000  $\mu\text{mol}$ ), 2.5 % Fe/ZSM-5 (30) (27 mg), 50 °C, 1500 rpm.

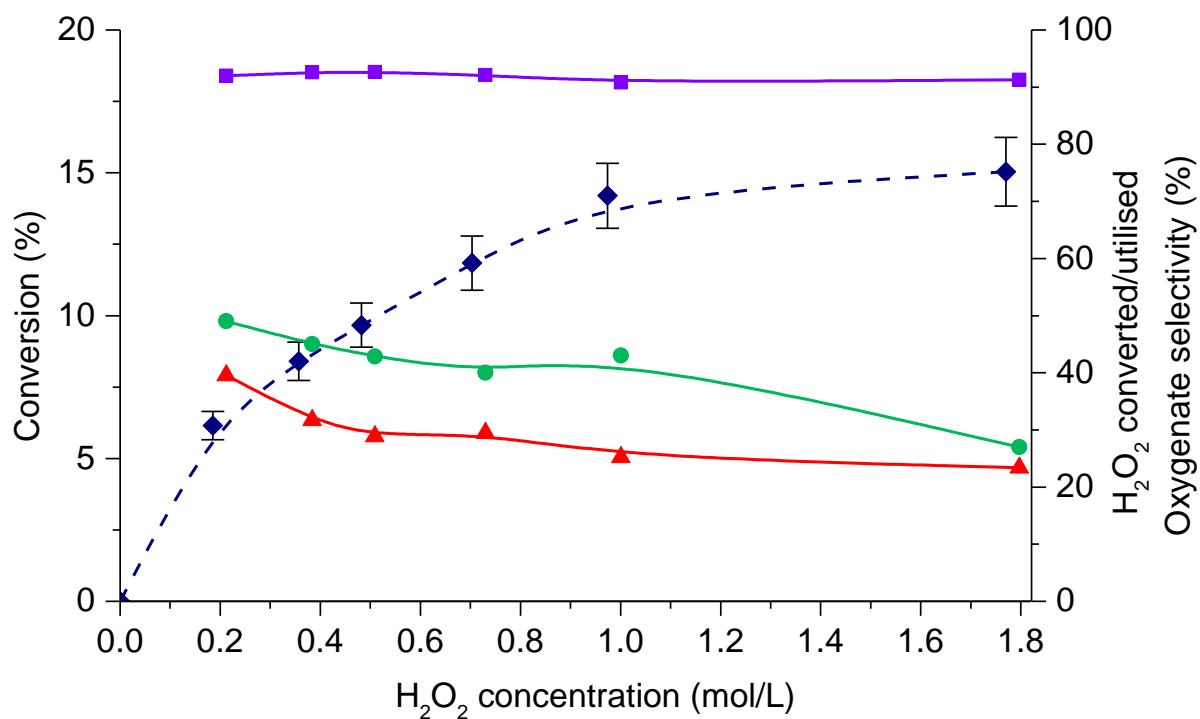


**Figure 5** – Effect of H<sub>2</sub>O<sub>2</sub> concentration for propane oxidation. Propane conversion (♦), oxygenate selectivity (■), H<sub>2</sub>O<sub>2</sub> converted (▲) and H<sub>2</sub>O<sub>2</sub> utilised (●). Reaction conditions: Propane (4000 μmol), H<sub>2</sub>O<sub>2</sub>, 2.5 % Fe/ZSM-5 (30) (27 mg), 50 °C, 0.5 h, 1500 rpm.

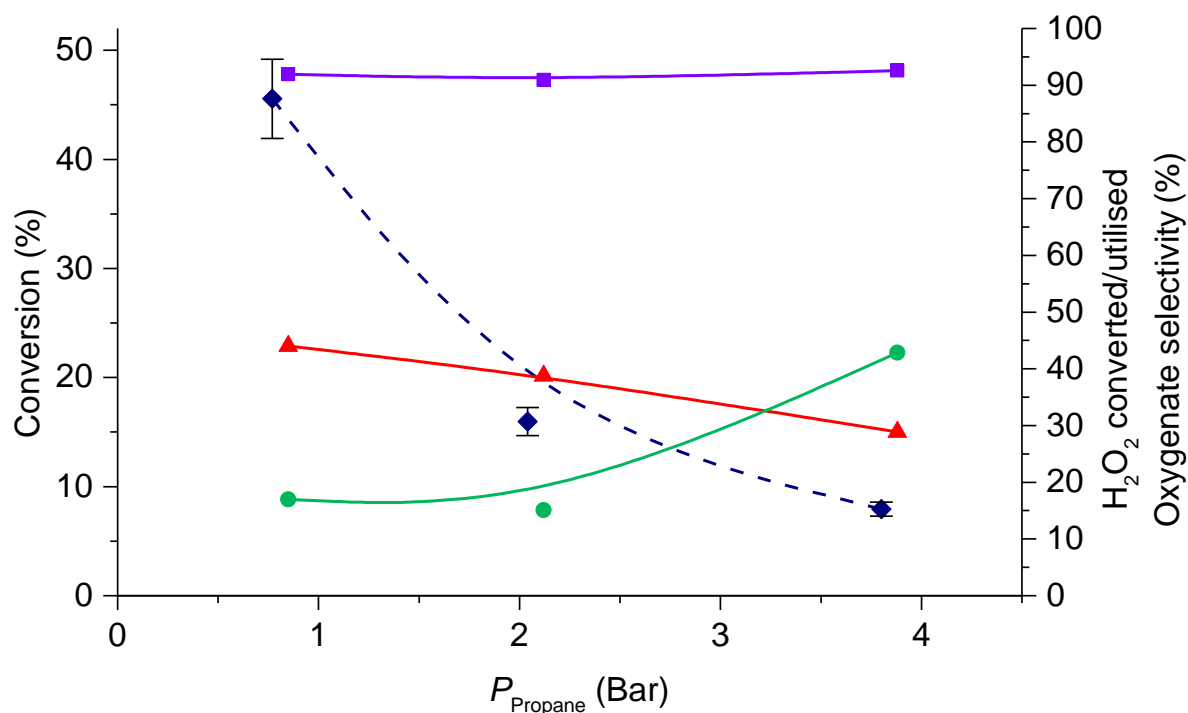


**Figure 6** – Effect of partial pressure of propane for propane oxidation. Propane conversion (◆), oxygenate selectivity (■),  $\text{H}_2\text{O}_2$  converted (▲) and  $\text{H}_2\text{O}_2$  utilised (●). Reaction conditions: Propane (4000  $\mu\text{mol}$ ),  $[\text{H}_2\text{O}_2] = 0.5 \text{ M}$  (5000  $\mu\text{mol}$ ), 2.5 % Fe/ZSM-5 (30) (27 mg), 50 °C, 0.5 h, 1500 rpm.




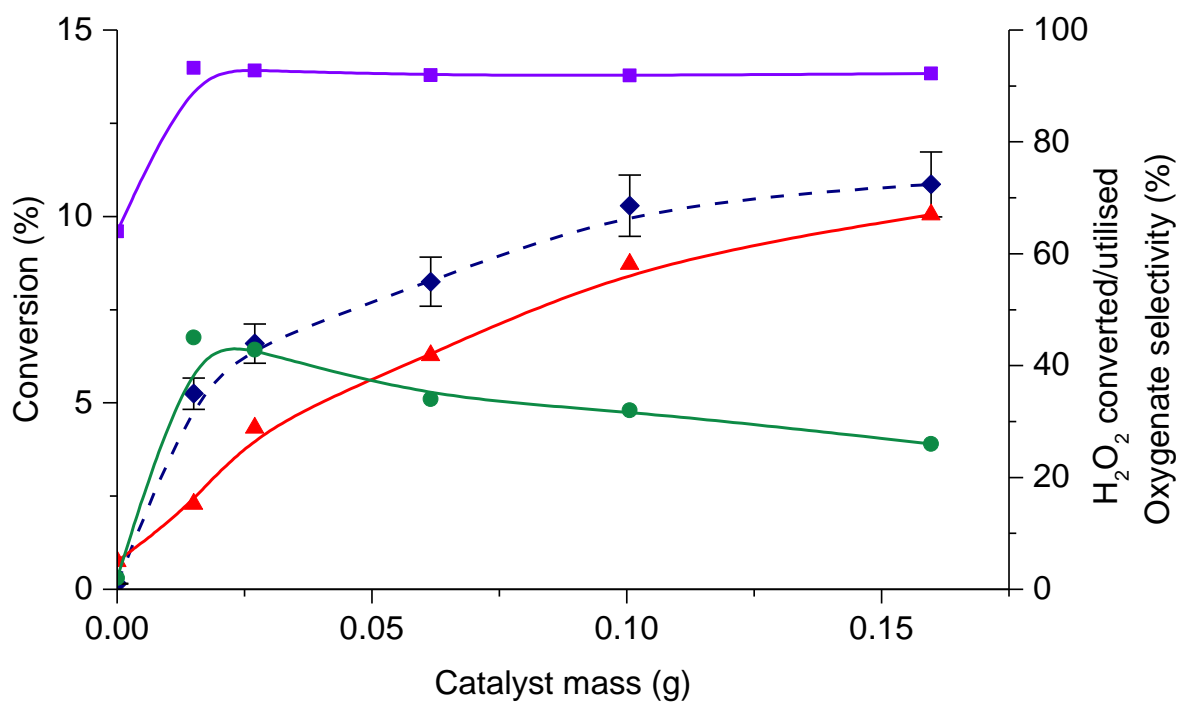

**Figure 7** – Effect of mass of catalyst for propane oxidation. Propane conversion (◆), oxygenate selectivity (■), H<sub>2</sub>O<sub>2</sub> converted (▲) and H<sub>2</sub>O<sub>2</sub> utilised (●). Reaction conditions: Propane (4000 μmol), [H<sub>2</sub>O<sub>2</sub>] = 0.5 M (5000 μmol), 2.5 % Fe/ZSM-5 (30), 50 °C, 0.5 h, 1500 rpm.

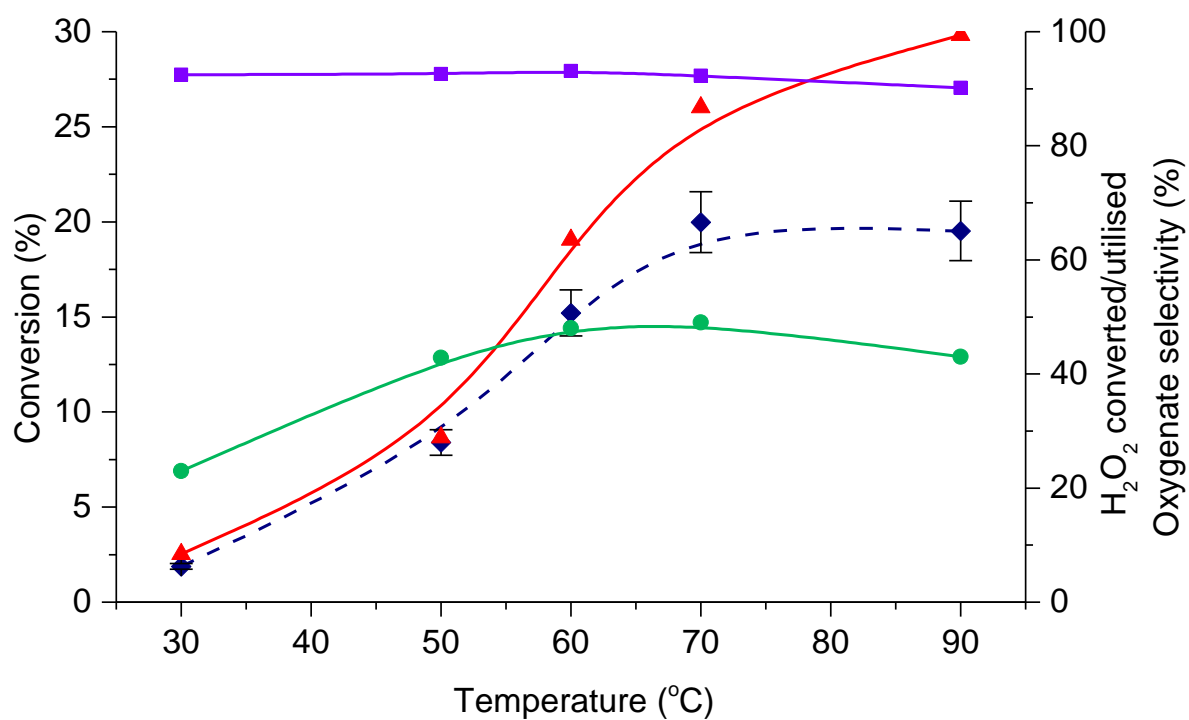

**Figure 8** – Effect of temperature for propane oxidation. Propane conversion (◆), oxygenate selectivity (■), H<sub>2</sub>O<sub>2</sub> converted (▲) and H<sub>2</sub>O<sub>2</sub> utilised (●). Reaction conditions: Propane (4000 μmol), [H<sub>2</sub>O<sub>2</sub>] = 0.5 M (5000 μmol), 2.5 % Fe/ZSM-5 (30) (27 mg), 0.5 h, 1500 rpm.

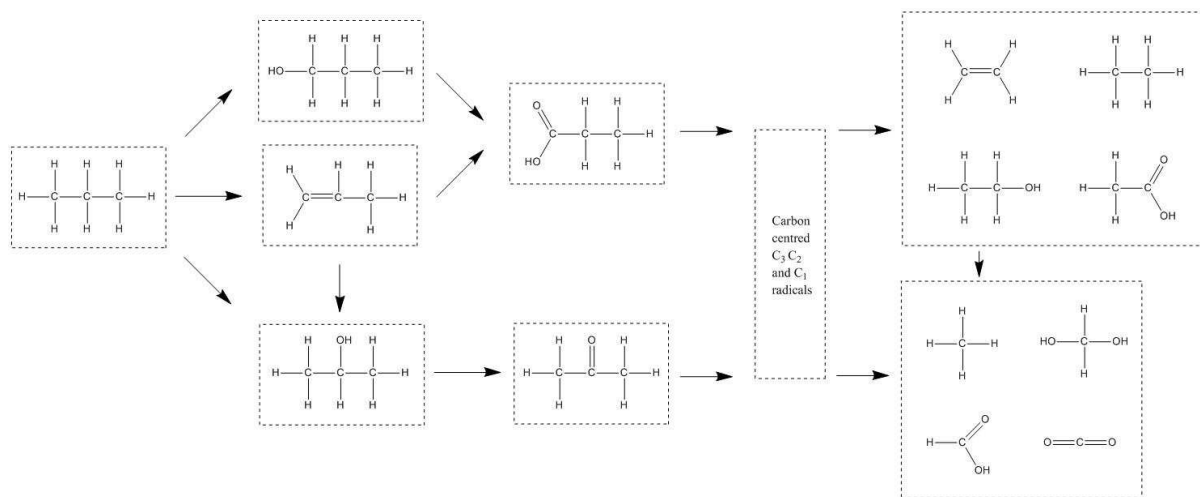

**Figure 9** – Reaction scheme for the oxidation of propane using  $\text{H}_2\text{O}_2$  in an aqueous medium.

**Table 2** Catalytic oxidation of propane under high conversion conditions using 2.5% Fe/ZSM-5 (30)

Entry	Propane conversion / %	H <sub>2</sub> O <sub>2</sub> Conversion / %	H <sub>2</sub> O <sub>2</sub> Utilisation / %	Product Selectivities / %														Combined Product Selectivity/ %	
				C3 Products				C2 Products				C1 Products							
				Acetone	<i>i</i> -PrOH	<i>n</i> -PrOH	Propanoic Acid	C <sub>3</sub> H <sub>6</sub>	EtOH	Acetic Acid	C <sub>2</sub> H <sub>4</sub>	C <sub>2</sub> H <sub>6</sub>	MeOH	Formic Acid	CH <sub>4</sub>	CO <sub>2</sub>	C <sub>3</sub>	C <sub>2</sub>	C <sub>1</sub>
1	7.9	29	43	6.4	5.7	8.8	11.4	2	14.1	11	0.6	1.5	1.3	34.6	0.9	1.4	33	28	39
2	33	99	29	8.0	0.2	0.8	7.0	0.6	1.2	25.3	0.2	0.7	0.8	43.8	0.4	10.7	17	27	56
3	19	52	27	9.7	1.8	2.9	8.7	1.4	5.4	20.1	0.3	2.0	1.2	40.4	1.1	5.0	24	28	48
4	23	75	26	10.1	1.9	2.3	7.7	0.9	3.6	23	0.3	1.6	1.1	40.4	1.5	5.5	23	28	49
5	52	97	12	1.6	0.0	0.0	0.0	0.02	0.0	33.9	0	0.2	0.2	29.5	0.2	34	2	34	64

Reaction conditions for Entry 1: Propane (4000  $\mu$ mol), [H<sub>2</sub>O<sub>2</sub>] = 0.5 M (5000  $\mu$ mol), 27 mg catalyst, 50 °C, 0.5 h, 1500 rpm.

Entry 2: Propane (4000  $\mu$ mol), [H<sub>2</sub>O<sub>2</sub>] = 1 M (10,000  $\mu$ mol), 100 mg catalyst, 70 °C, 0.5 h, 1500 rpm.

Entry 3: Propane (4000  $\mu$ mol), [H<sub>2</sub>O<sub>2</sub>] = 1 M (10,000  $\mu$ mol), 100 mg catalyst, 50 °C, 0.5 h, 1500 rpm.

Entry 4: Propane (4000  $\mu$ mol), [H<sub>2</sub>O<sub>2</sub>] = 1 M (10,000  $\mu$ mol), 100 mg catalyst, 50 °C, 2 h, 1500 rpm.

Entry 5: Propane (800  $\mu$ mol), [H<sub>2</sub>O<sub>2</sub>] = 1 M (10,000  $\mu$ mol), 100 mg catalyst, 70 °C, 2 h, 1500 rpm.

**Table 3** Catalytic conversion of C<sub>3</sub> products under propane reaction conditions.

Reactant	Conversion / %	Amount of Product/ $\mu\text{mol}$					Rate / $\text{mol}_{\text{converted}} \text{kg}_{\text{cat}}^{-1} \text{h}^{-1}$	TOF / $\text{mol}_{\text{Fe}}^{-1} \text{h}^{-1}$
		Acetone	Propanoic	Acetic Acid	Formic Acid	CO <sub>2</sub>		
<i>n</i> -PrOH <sup>[a]</sup>	47	0.6	19	13	92	12	261.1	583.3
<i>i</i> -PrOH <sup>[a]</sup>	93	58	-	99	218	14	516.7	1154.1
Acetone <sup>[a]</sup>	62	-	-	70	62	17	344.4	769.4
Propanoic acid <sup>[a]</sup>	12	-	-	17	22	9	66.7	148.9
Propanoic acid <sup>[b]</sup>	43	-	-	47	108	38	16.0	35.6

Reaction conditions:  $[\text{H}_2\text{O}_2] = 0.5 \text{ M}$  (5000  $\mu\text{mol}$ ), 27 mg 2.5% Fe/ZSM-5 (30), P(He) = 20 bar, 50 °C, 1500 rpm. <sup>[a]</sup>Reaction time: 2 min, <sup>[b]</sup> Reaction time: 0.5 h

**Table 4** The effect of copper addition upon the catalytic performance of 1.25% Fe/ZSM-5 (30) in propane oxidation

Entry	Cu loading / wt%	Propane conversion / %	H <sub>2</sub> O <sub>2</sub> conversion / %	H <sub>2</sub> O <sub>2</sub> utilisation / %	Product Selectivities / %												Combined Product Selectivity / %			
					C3 Products			C <sub>2</sub> Products			C <sub>1</sub> Products									
					Acetone	<i>i</i> -PrOH	<i>n</i> -PrOH	Propanoic Acid	C <sub>3</sub> H <sub>6</sub>	EtOH	Acetic Acid	C <sub>2</sub> H <sub>4</sub>	C <sub>2</sub> H <sub>6</sub>	MeOH	Formic Acid	CH <sub>4</sub>	CO <sub>2</sub>	C <sub>3</sub>	C <sub>2</sub>	C <sub>1</sub>
1	0	5.9	19	56	6.8	7.5	12.6	9.0	1.8	18.0	9.2	0.3	2.0	1.3	29.0	1.1	1.3	38	31	33
2	0.4	4	22	30	6.4	8.3	18.1	7.9	0.8	21.3	6.6	0.2	1.4	1.2	27.2	0.3	0.2	42	31	29
3	1.25	3.9	27	13	6.7	8.5	16.4	9.2	24.3	16.3	6.5	5.2	1.3	1.3	0.0	3.1	1.1	64	30	6
4	2.5	2.6	7	36	7.8	8.8	14.9	5.4	33.7	9.6	0.0	5.0	1.7	1.0	10.7	0.1	1.1	71	16	13

Reaction conditions: Propane (4000 μmol), [H<sub>2</sub>O<sub>2</sub>] = 0.5 M (5000 μmol), 27 mg catalyst, 50 °C, 0.5 h, 1500 rpm

**Table 5** Propane conversion catalysed by 1.25 %Fe-1.25 %Cu / ZSM-5 (30) under high conversion conditions.

Entry	Propane conversion / %	H <sub>2</sub> O <sub>2</sub> conversion / %	H <sub>2</sub> O <sub>2</sub> utilisation / %	Product Selectivities / %													Combined Product Selectivity/ %		
				C3 Products				C2 Products				C1 Products							
				Acetone	<i>i</i> -PrOH	<i>n</i> -PrOH	Propanoic Acid	C <sub>3</sub> H <sub>6</sub>	EtOH	Acetic Acid	C <sub>2</sub> H <sub>4</sub>	C <sub>2</sub> H <sub>6</sub>	MeOH	Formic Acid	CH <sub>4</sub>	CO <sub>2</sub>	C <sub>3</sub>	C <sub>2</sub>	C <sub>1</sub>
1	3.9	27	6	6.7	8.5	16.4	9.2	24.3	16.3	6.5	5.2	1.3	1.3	0.0	3.1	1.1	64	30	6
2	17.6	89	8	11.8	2.0	6.3	7.2	13.1	9.1	30.4	6.1	0.8	3.9	0.0	0.8	7.9	40	46	13
3	9.2	40	7	10.0	4.4	10.8	7.9	20.6	13.8	16.9	6.8	1.3	3	0.0	0.7	3.5	53	39	8
4	12.3	58	8	10.7	3.8	8.7	9.2	15.4	11.7	22.3	6.3	1.7	3.2	0.0	1.2	5.7	48	42	10

Reaction conditions for Entry 1: Propane (4000  $\mu$ mol), [H<sub>2</sub>O<sub>2</sub>] = 0.5 M (5000  $\mu$ mol), 27 mg catalyst, 50 °C, 0.5 h, 1500 rpm.

Entry 2: Propane (4000  $\mu$ mol), [H<sub>2</sub>O<sub>2</sub>] = 1 M (10,000  $\mu$ mol), 100 mg catalyst, 70 °C, 0.5 h, 1500 rpm.

Entry 3: Propane (4000  $\mu$ mol), [H<sub>2</sub>O<sub>2</sub>] = 1 M (10,000  $\mu$ mol), 100 mg catalyst, 50 °C, 0.5 h, 1500 rpm.

Entry 4: Propane (4000  $\mu$ mol), [H<sub>2</sub>O<sub>2</sub>] = 1 M (10,000  $\mu$ mol), 100 mg catalyst, 50 °C, 2 h, 1500 rpm

